EXPERIMENTAL STUDY OF PANEL PRECAST BUTON ASPHALT PAVEMENT WITH STRENGTHENED BY GEOGRID

[1]SUNARYO MULYO, [2]HERMAN PARUNG, [3]AHMAD BAKRI M, [4]RUDY DJAMALUDDIN

Doctoral Postgraduate Student of Civil Engineering, Hasanuddin University
E-mail: sunaryo@baubaukota.go.id

Abstract— Precast buton asphalt panels with the same characteristics as the characteristics of the massive asphalt can be used as an alternative method of implementation of the asphalt pavement as an effort to simplify and reduce of implementation errors, so that it can increase the attractiveness of the use of asphalt Buton. With the results of experimental tests of the model of precast panels Buton Asphalt pavement is known that the geogrid is able to raise the Buton asphalt panel's ability to withstand a static load and increase the stiffness of the panel. This will be very beneficial related to the real conditions on the field that the pavement was often got static load like a wheel load of vehicles that are parked or load of the panel itself while in the process of transporting and stacking. The most effective is installed on a panel with a thickness of 5 cm. It is seen an increase in the percentage of the maximum static load bearing capability as well as an increase in the amount of deflection before collapse.

Keyword— Buton Aspal, Precast, Panel, Geogrid.

I. INTRODUCTION

Buton asphalt or called Asbuton, a natural asphalt of Buton Island with the largest deposits in the world when compared to other natural bitumen deposits, is also one of Indonesia's natural resources potential as an ingredient mix asphalt pavement. Utilization Asbuton on the pavement has long encouraged the Government of Indonesia both Asbuton Kabungka (Asbuton of deposits in the District Kabungka) or Asbuton Lawele derived from Lawele District of Buton. However, the use of asbuton not as expected because of a failure in the implementation of Asbuton such as consistency or uniformity factor Asbuton quality, equipment factors, accuracy of mix design, as well as quality control in the field. Due to the failure of the quality of the pavement of Asbuton inadequate and destroyed before reaching the age of plans. With so many failures the implementation of the field and price competition compared with asphalt oil when the price of crude oil in normal conditions is almost equal, then make Asbuton less desirable for use as road pavement material.

Asbuton as natural asphalt when used for hot mix asphalt must have been conditioned so they can go in and mixed well with the aggregate and asphalt oil, to be used as ingredients added before processing should be done first. Madi Hermadi (2008), states that based on studies in laboratory Specifications Hot Asphalt Mixture Asbuton Lawele to note are as follows:

a) Aggregate nature and properties of the mixture referring to the requirements of Hot Asphalt Mixture in general.
b) Asbuton Lawele used for Hot Asphalt Mixture is Asbuton Lawele that are processed or conditioned in such a way (fabrication) that Asbuton Lawele have homogeneous properties and meet specific requirements.
c) Lawele Asbuton requirements should be such as to accommodate the processing of simple ways that inexpensive yet quality Asbuton Lawele ensuring compliance with the desired quality of pavement that has a shape that is easy to apply and produces a mixture with good characteristics.
d) At Asbuton processing Lawele light oil is not removed entirely but rather only until a bitumen with a penetration of 60-79 dmm value. Thus, processing is simpler than having to spend the whole light oil. In addition, because it has a value of 60-79 dmm penetration bitumen, or is equivalent to the value of the penetration of petroleum asphalt for pavement pen 60, then the views of the value of penetration in principle bitumen asphalt Asbuton Lawele could substitute oil to 100%.
e) To anticipate dryness bitumen Asbuton Lawele due to the evaporation of light oil remains, both upon heating in Unit Mixing Asphalt (AMP) as well as during isntalled until the service will be limited bitumen Asbuton Lawele after weight loss with Thin Film Oven Test (TFOT), which means after the light oil is lost, should have a penetration that is still decent value for pavement that is the minimum penetration 40. This limitation refers to the requirements of Natural Asphalt Modified Asphalt with the limit values and the penetration of 40-55 dmm Pure Asbuton requirements to limit the penetration of 40-60 dmm value. If the value is not achieved or the penetration bitumen Asbuton Lawele after TFOT lower than 40 dmm, it will be added to asphalt to meet the requirement and also become the benchmark levels Lawele Asbuton maximum. While Asbuton Lawele optimum levels will be determined after reviewing the

donations also mineral Asbuton Lawele into the mix gradation.

f) To facilitate the implementation of the mix design with Marshall procedure and to safeguard the fulfillment of the criteria of filler to bituminous ratio, Asbuton Lawele will be pegged at certain levels (according to the results of the study of the properties of bitumen and grading) while to get the binder content in total optimum, which varied are the levels of tar oil added.

g) In order not to complicate the implementation of the field, which is used Lawele Asbuton products required to be in the form of grains so easily supplied into Pugmill in AMP through the silo filler or through a special bin. The maximum grain size should also be certain that mixing times faster than Asbuton Lawele form large clumps.

In general, the road pavement can be classified into three major categories, namely: flexible pavement, rigid pavement, composite pavement. For rigid pavement systems is currently not only used on site or treated in the workplace, also used the system off site called precast. The advantage of the use of this method are: saving time implementation, manufacturing precast panels will ensure the consistency of the mix and raise the level of quality control, economic benefits obtained, and the road can be immediately used by the public. Besides, it also saves maintenance costs and other extra costs during the construction process.

With the various advantages of using precast concrete for pavement, then it certainly can be applied also to the asphalt pavement. Buton asphalt with a panel that made of off site, the expected gains in the use of precast concrete also occurs in models of panel precast asphalt used as road pavement. Moreover, it can encourage the use of Buton asphalt for road pavement.

Geogrid is one type of geosynthetic materials that have woven a large hole and stiffness better than Geotextile. Geogrid base material are Polyphropylene, Polyethylene, Polyesther, or other polymer material. Geogrid can serve reinforcement in pavement layers. With the " woven hole' relatively large (1-4 cm), Geogrid can lock the aggregate between "hole" which can increase the rigidity of the aggregate layer. The main function of the geogrid reinforcement is to strengthen the aggregate layer to provide a high tensile strength values at low strain value and to limit the aggregate layer so it will not move in the lateral direction so as to reduce the magnitude of the radial strain on the asphalt layer. This condition will certainly extend the service life of the pavement structure.

Ability geogrids provide tensile strength to the layer of asphalt concrete can also be done by testing the asphalt concrete beams were given concentrated static load continuously until the collapse of the asphalt concrete beam. The use of static load in this test to simulate the load of a vehicle that was stopped. At the time of receiving the asphalt concrete beams concentrated load, the lower beam section will receive a tensile stress. Tensile stress that occurs will be retained by the geogrid is installed at the bottom of asphalt concrete beam section. Geogrid tensile strength and shear strength between the geogrid and asphalt concrete will serve withstand tensile stress occurs in he lower beam section. Difference maximum load at the time of the collapse of the asphalt concrete reinforced with geogrid with asphalt concrete without reinforcement geogrid is the ability to withstand tensile stresses that occur at the bottom of asphalt concrete face (figure 1). This test can also be used to determine the maximum deflection which can occur in asphalt concrete before the collapse due to vertical load.

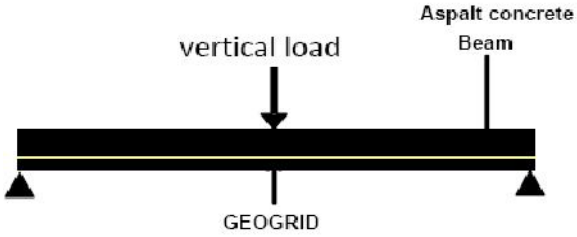


Figure 1. Scheme of Testing Capabilities Asphalt Pavement Materials

Traffic load will cause the layer of asphalt concrete pavement flexible. By the time the bottom sagged at the bottom of the road pavement structure will occur tensile and compressive stress on the top of the pavement. Layer of pavement will be back again to its original position after moving vehicle wheel load. Giving tensile strength can be done with the installation of geogrid at the bottom of the asphalt concrete pavement that will provide resistance to tensile stresses that occur on pavement while receiving traffic load. The resistance provided by the geogrid will reduce bending at the pavement when receiving the load wheel so as to increase the strength of the static load and the load receiving moving. Vertical pressure caused by the load wheels of the vehicle will cause geogrid which sagged under the wheels of the vehicle. Tensile stress geogrid geogrid position will restore to its original position, resulting in resistance to shear force generated by the load wheels of the vehicle. Tensile modulus geogrid will greatly affect the ability to maintain the pavement ruts vehicle (Widodo, Sri, 2012). Based on the above-mentioned to think about ways of implementing flexible pavement Buton asphalt is simple and does not require much equipment, as well as implementing the expert, but still ensuring compliance with the quality of the desired quality of the pavement and has a shape that is easy to apply. Furthermore Asphalt pavement is also utilized as a mixture Buton

additional efforts to increase its use in flexible pavement.

For this purpose need experimental studies of a model of Buton asphalt pavement type precast panel with geogrid reinforcement as efforts to develop new innovations in the construction of the road surface with a material layer Asbuton.

II. RESEARCH METHOD

Research to be conducted is a purely experimental research in the form of laboratory studies. Research conducted in the laboratory of Transport Engineering Department of Civil Engineering, Faculty of Engineering, University of Hasanuddin Makassar.

The materials to be used in this study include:

a) Aggregate coarse, derived from rocks Ex. Bili-Bili Gowa. the breakdown of the stone (stone crusher) PT Cipta Pratama Garungga South Sulawesi).
b) Fine aggregate using river sand Jeneberang Gowa in South Sulawesi.
c) Fly ash comes from Batu Ex. Bili-Bili Gowa. the breakdown of the stone (stone crusher) PT Cipta Pratama Garungga South Sulawesi
d) Lawele Granular Asphalt (LGA) which is used as a mixture is produced from PT. Buton Asphalt Indonesia (PT BAI) Lawele Asphalt from Buton Buton in Southeast Sulawesi.
e) For materials using bitumen Pertamina asphalt with penetration 60/70.
f) For the type biaxial geogrid Geogrid used that E'Grid of Geoforce Indonesia (www.geoforceindonesia.com).

Use hot asphalt mixing system Asphalt Concrete-Wearing Course (AC-WC) with a guide The Asphalt Institute (1997) Superpave Series No. 1 (SP-1) which is the basis of the construction of highways and widely used by DGH. Whereas testing standards used in part using a standard issued by the Asphalt Institute (1997) Superpave Series No. 1 (SP-1) but most adopt of methods validated or standardized by ISO Highways form. Most of bitumen can be substitution of asphalt in the asphalt mix concrete.

In the tests carried out in stages, consisting of initial testing to determine the optimum bitumen content in order to obtain a mixture of asphalt mix design. From this initial test was obtained the optimum bitumen content of 6.5% by Lawele Buton asphalt content of 10%. Furthermore, the composition of the mixture is made model of panel size 40 x 30 cm and compacted / pressed to obtain optimum density according to initial testing. The model consists of two types, reinforced with geogrid and are not reinforced with geogrid. Furthermore, both types of test specimens were tested to determine the static load deflection and strain that occurs.

A. Equipment

Equipment used for testing precast panel consists of: Panel Molding Apparatus with compacting equipment; Universal Testing Machine (UTM) is a testing machine to test the tensile and compressive strength of the material; Linear Variable Differential Transformers (LVDT), used 6 pieces LVDT to measure the deflection. The equipments are connected to a computer so that it can be read directly load and deflection value; TDS 7130, is a equipment for recording the measurement data LVDT connected directly to the computer.

B. Testing Material

The model measuring 40 cm X 30 cm, with varying thickness are 4 cm, 5 cm and 6 cm. Consisting of panel without reinforcement geogrid, and a panel with geogrid reinforcement. In this study, for panels with reinforcement geogrid material geosynthetic is placed in the bottom panel of the idealization of conditions in the field as well as with reference to the experiment Moussa (2003) that the location of the geotextile at the bottom who are in the middle layer of binder course provide reinforcement greatest.

C. Testing Procedure

Testing of materials, including, asphalt Buton, Coarse and Fine Aggregate to obtain the characteristics of each material. The next test for various mixtures of the mix asphalt concrete (ACWC) to obtain the optimum bitumen content as a guideline in the create of test specimens of asphalt panel; Creating a sample model of panel size 40 x 30 cm with a thickness varying; Putting the sample in the position that has been set mileage; Installing a TDS LVDT connect with tools that have been associated with computer; Using software TDS 7130, then the contents of commands that should be included in it, as required; Run UTM instrument to do the reading on TDS software to stop providing UTM appliance load.

III. TEST RESULT AND DISCUSION

Before the main testing, have been tested and the initial examination. After the initial examination showed that the aggregate will be used as a mixture of asphalt in accordance with SNI (Indonesia National Standart). Inspection includes examination of: density, gradation, flakiness, material hardness, water absorption. The overall characteristics of the material qualified. Optimum Asphalt levels gained 6.5% with the content of Buton Asphalt Lawele 10%. based on asphalt mix designs created panel size 40 cm x30 cm with and without reinforcement geogrid.

Testing panel without geogrid asphalt or reinforced with geogrid to do the panel by 4cm thick, 5cm and 6cm, The result of testing as seen Table 1, it can be seen that for a maximum load of each sample occurs by an additional reinforcement or increased ability to withstand loads due to the addition of geogrid as

follows; For panel 4 cm an increase of 122.22%; 5 cm thick panels for an increase of 133.71%; and 6 cm thick panels for an increase of 109%. When compared to the three of thickness, 5 cm thick panels have a higher increase than the panel with a thickness of 4 cm and 6 cm.

Similarly, when viewed from panel's deflection with a thickness of 5 cm then the panel without reinforcement and panels with geogrid reinforced has a greater deviation than the other two samples. That is the effectiveness of geogrid to increase the ability of asphalt deflection due to static load on the sample panel 5 cm thick were higher compared with the sample thickness of 4 cm and 6 cm. Of the overall test results show that a thickness of the asphalt affect the load bearing capability. The thicker of asphalt layer, the greater the load that can be accepted by the asphalt layer. It can be seen from the data that is generated on a deflection test table where average of value P max sample with a sample thickness of 4 cm, 5 cm and 6 cm queried sequence is equal to 84 N, 400.67 N and 554.67 N. (Table. 1)

Table.1. Results of Static Load Testing and Deflection

No	Sample	P Max	Deviation	Deflection Max	Deflection Max	Deflection Max
		N	%	Left Span	Middle Span	Right Span
1	4 Normal	84,00	122,22%	3,90	5,90	3,35
2	4 + G	186,67		6,49	10,97	7,90
Deviation				66,36%	85,85%	135,93%
3	5 Normal	400,67	133,71%	4,00	5,66	3,46
4	5 + G	936,40		11,25	16,51	10,84
Deviation				181,59%	191,58%	213,80%
5	6 Normal	554,67	109,63%	3,58	4,67	3,66
6	6 + G	1162,77		8,62	13,28	9,35
Deviation				140,67%	184,59%	155,36%

Normal = Panel Without Geogrid Reinforcement; G = Panel Reinforced with Geogrid

Normal = Panel Without Geogrid Reinforcement; G = Panel Reinforced with Geogrid The test result also showed that addition of geogrid in asphalt layers can improve the ability to accept larger loads, because the flexibility of geogrid can maintain the position of the layer when it receives load. The percentage increase between the samples of 4 cm compared 4 cm + Geogrid amounted to 122.22%, while the percentage increase between the samples of 5 cm compared 5 cm + Geogrid amounted to 133.71%, and the percentage increase between the sample 6 cm compared 6 cm + geogrid is equal to 109.63%.

CONCLUSION

With the results of experimental test of the model of precast panels Buton Asphalt pavement, it can be concluded that further increase the value of the layer thickness deflection of will decrease, because the level of flexibility of a aspalt layer decreases with the increase of the thickness of a layer. Geogrid is able to raise the Buton asphalt panel's ability to withstand a static load. This will be very beneficial associated with the real conditions in the field that often gets pavement static load like a wheel load of vehicles that are parked or load of the panel itself while in the process of transporting and stacking.

The most effective geogrid is installed on a panel with a thickness of 5 cm. It is seen an increase in the maximum static load bearing capabilities as well as an increase in the amount of deflection before the collapse.

Buton asphalt panels with the same characteristics as the characteristics of a massive expanse of asphalt will be used as an alternative method of implementation of the asphalt pavement as an effort to reduce error in the field implementation and can increase the attractiveness of Buton aspalt use.

REFERENCES

[1] Adhikari.S & You.Z, 2010, Fatigue Evaluation of Asphalt Pavement Using Beam Fatigue Apparatus, Technology Interface Journal, 2010. Vol. 10. No.3.

[2] Alamsyah Alik Ansyori, 2001, Rekayasa Jalan Raya, Universitas Muhammadiyah Malang, Malang..

[3] Hermadi Madi, M. Sjahdanulirwan, 2008, Usulan Spesifikasi Campuran Beraspal Panas Asbuton Lawele Untuk Perkerasan Jalan, Jurnal Puslitbang Jalan dan Jembatan, Bandung

[4] Howardy, Latif Budi Suparma, Iman Satyarno, 2008, Perencangan Laboratorium Campuran HRS WC dengan Penggunaan Buton Granular Aspal (BGA) sebagai additive, Jurnal Teknik Sipil Vol. 18.No.3.

[5] Kurniati Inna, dkk, 2003, Aplikasi Teknologi Geosintetik Untuk Perkerasan Lentur, Jurnal Teknosains 16(B), Yogyakarta.

[6] Manu Agus Iqbal, 2002, Pelaksanaan Konstruksi Jalan Raya, Safir Alam, Jakarta

[7] McCullough B Frank, Ph.D., P.E, David K. Merritt, P.E., Ned H. Burns, Ph.D., P.E, 2005, Design- Construction of a Precast, Prestressed Concrete Pavement for Interstate 10,

El Monte, Federal Highway administration's Concrete Pavement Technology Programe, California.

[8] Moussa, G.K.M., 2003, The Optimum Location of Geotextile Reinforcement in Asphalt Layers, Alexandria Engineering Journal Vol.42 No.1 pp.103-111, Faculty of Engineering Alexandria University, Egypt.

[9] Nugroho Soewignjo Agus, 2006, Variasi Kadar Aspal Pada Perkerasan Lentur Diperkuat Dengan Geosintetik, Jurnal Media Komunikasi Teknik Sipil Volume 14, No. 3, Edisi Xxxvi Oktober Universitas Riau, Pekanbaru.

[10] Sjahdanulirwan, 2008, Kelebihan serta Kekurangan Perkerasan Beraspal dan Beton, Puslitbang Jalan dan Jembatan, Bandung.

[11] Soehartono, Ir, 2010, Teknologi Aspal dan Penggunaannya dalam Konstruksi Perkerasan Jalan,Badan Penerbit Pekerjaan Umum, Jakarta.

[12] Suaryana Nyoman, 2008, Analisis Faktor-Faktor Yang Mendorong Kegagalan Dalam Pelaksanaan Asbuton, Puslitbang jalan dan Jembatan, Bandung.

[13] Sukirman Sinvia, 2003, Beton Aspal Campuran Panas, Granit, Jakarta.

[14] Sutoyo dan Pinardi K, 2010, Perancangan Tebal Perkerasan jalan Jenis Lentur dan Jenis Kaku, Badan Penerbit Pekerjaan Umum, Jakarta.

[15] Widodo Sri, dkk, 2012, Analisis Modulus Elastisitas Beton Aspal Yang Diperkuat Dengan Geotekstil dari Hasil Uji Tekuk Batang, Dinamika TEKNIK SIPIL/Vol. 12/No. 2/Mei 2012, Semarang.

[16] Widodo Sri, dkk, 2012, Potensi Geosintetik Sebagai Perkuatan Lapis Perkerasan Lentur Jalan Raya, Universitas Dipone-goro, Semarang

[17] Ismanto Bambang, Kusnianti Neni, Tumewu Willy, Laboratory Evaluation Of Lawele Buton Natural Asphalt In Asphalt Concrete Mixture, Puslitbang jalan, Bandung, 2005.

★★★